



ON THE BECQUEREL EFFECT OF COPPER OXIDE ELECTRODE IN ALKALI SOLUTION.*

Some Considerations from the Stand-points of
Reaction Kinetics and Thermodynamics.

By NAGAO HAYAMI.

Since the discovery of the Becquerel effect¹⁾ of a copper oxide electrode, many studies²⁾ have been made on the effect and yet there was no satisfactory theory to elucidate the mechanism of the effect because of disagreement in experimental results. Several years ago, Prof. S. Horiba and the author³⁾ found that the disagreement was due to the fact that those studies were undertaken with the copper oxide electrodes not in complete equilibrium, and so they investigated the effect with the copper oxide electrode considered to be in complete equilibrium and proposed a theory on the effect. Long after cuprous oxide film was immersed in alkali solution, a black cupric oxide film was obtained by the catalytic action of alkali. The copper oxide electrode thus obtained presented a constant voltage in the dark, that is, it was regarded as an electrode in such an equilibrium as $2\text{CuO} \rightleftharpoons \text{Cu}_2 + \frac{1}{2}\text{O}_2$. Using this electrode, Prof. S. Horiba and the author studied the Becquerel effect of the following two cells:



and observed that the effect was simply owing to the photo-reversible reaction:

* This paper is the English translation of the same article which appeared in *this journal*, 9, 38 (1934).

1) Becquerel, *La Lumiere*, 11, 121; C. R., 9, 561 (1839).

2) Rigollot, *Annalis de l'Université de Lyon*, 29, Mai (1891).

Goldmann & Brodsky, *Ann. Physik.*, [4], 849 (1914); *ibid*, 44, 914 (1914).


Bauer, *Z. Physik. Chem.*, 66, 683 (1908); *ibid*, 72, 323 (1910).

A. D. Garrison, *J. phys. Chem.*, 27, 601 (1923).

A. Tucker, *ibid*, 31, 1356 (1927).

Wildermann, *Z. physik. Chem.*, 59, 708 (1906); *ibid*, 62, 70 (1907).

3) S. Horiba and N. Hayami, *Rev. Phys. Chem. Japan*, 4, 55 (1930).



Experimental.

1) Material and Procedure.

Experimental Results.

Expt. I. Measuring Instrument and Change of Photovoltaic Potential with Time.

The photovoltaic potentials calculated by means of a potentiometer are given in Table I, a, and those by means of a quadrant electrometer in Table I, b; these are compared in Fig. 1.

Table I, a.

The Influence of the Measuring Instrument on the Photovoltaic Potential.

Time (mins.)	E. M. F. of Cell [A] (volts.)	Photovoltaic Potential (mili-volt.)	$\left((E. M. F. \text{ of } Cu Cu_2O, CuO, \frac{N}{10}NaOH H_2) \right)^{41}$ (volts)	PO_2 (oxygen- pressure) (atm)
Exposure				
0	0.2322	0	0.8425	1.000×10^{-26}
1	0.2476	15.4	0.8579	1.096×10^{-25}
2	0.2525	20.3	0.8628	2.399 "
4	0.2568	24.6	0.8671	5.754 "
6	0.2586	26.4	0.8689	6.310 "
8	0.2595	27.3	0.8698	7.244 "
10	0.2601	27.9	0.8704	7.762 "
12	0.2607	28.5	0.8710	8.710 "
15	0.2607	28.5	0.8710	8.710 "
30	0.2607	28.5	0.8710	8.710 "

4) The E. M. F. of $\text{Cu}/\text{Cu}_2\text{O}$, $\text{CuO} \frac{N}{10} \text{NaOH} \parallel \text{H}_2$, at $25^\circ \pm 0.02^\circ\text{C}$. (See S. Horiba and N. Hayami, *ibid.*), can be calculated from the E. M. F. of the cell (A) and E_h as follows:

E. M. F. of Cell (A)		Eh	
0°C	$\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{N}{10} \text{NaOH} 3N \text{NaOH} \frac{N}{10} \text{KCl}, \text{Hg}_2\text{Cl}_2 \text{Hg}$	$[\text{Hg} \text{Hg}_2\text{Cl}_2, \frac{N}{10} \text{KCl} 3N \text{NaOH} \frac{N}{10} \text{NaOH} \text{H}_2]$	
0°	0.2446 volt	1.0986 volt	
25°	0.2326 "	1.0747 "	
0°C	E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{N}{10} \text{NaOH} \text{H}_2$		
0°	0.8540 volt		
25°	0.8421 "		

Light off				
0	0.2607	28.5	0.8710	8.710×10^{-25}
2.5	0.2555	23.3	0.8658	3.802 "
3	0.2523	20.1	0.8626	3.396 "
5.5	0.2495	17.3	0.8598	1.489 "
7	0.2477	15.5	0.8580	1.125 "
7.5	0.2462	14.0	0.8565	1.038 "
8.5	0.2450	12.8	0.8553	7.379×10^{-26}
10	0.2432	11.0	0.8535	5.152 "
11	0.2413	9.1	0.8516	4.140 "
12.5	0.2392	7.0	0.8495	2.980 "
14.5	0.2370	4.8	0.8473	2.113 "

$25^{\circ} \pm 0.02^{\circ}\text{C}$. Light source: a 100V-200W Tungsten-filament lamp, operating from a battery supply. The light was passed through a 80 mm. layer of a Solution $(\text{CuSO}_4 + 1080 \text{ NH}_3)/90$ (Normal). Intensity of Light: $0.2364 \text{ cal/cm}^2/\text{sec}$. The measuring instrument: Leads & Northrup Potentiometer

Table II, b.

The Influence of the Measuring Instrument on the Photovoltaic Potential.

Time (mins.)	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \text{H}_2$) (volts)	Po ₂ (oxygen pressure) (atm)
Exposure				
0	0.2322	0	0.8425	1.000×10^{-26}
1	0.2522	20.0	0.8625	2.239×10^{-25}
2	0.2550	22.8	0.8653	3.467 "
4	0.2583	26.1	0.8686	5.754 "
6	0.2599	27.7	0.8702	7.567 "
8	0.2611	28.9	0.8714	9.084 "
10	0.2621	29.9	0.8724	1.072×10^{-24}
15	0.2621	29.9	0.8724	1.072 "
30	0.2621	29.9	0.8724	1.072 "
Light off				
0	0.2621	29.9	0.8724	1.072×10^{-24}
1.2	0.2598	27.6	0.8701	7.413×10^{-25}
2	0.2585	26.3	0.8688	6.025 "
3	0.2561	23.9	0.8664	4.169 "
4	0.2530	21.8	0.8643	3.020 "
5.5	0.2516	19.4	0.8619	2.042 "
6.5	0.2474	17.2	0.8597	1.479 "
7.5	0.2472	15.0	0.8575	1.047 "
8.5	0.2452	13.0	0.8555	7.585×10^{-26}
10	0.2428	10.6	0.8531	5.370 "
12	0.2405	8.3	0.8508	3.631 "
13.5	0.2383	6.1	0.8486	2.571 "

$25^{\circ} \pm 0.02^{\circ}\text{C}$. Light source: a 100V-200W Tungsten-filament lamp, operating from a battery supply. The light was passed through a 80 mm. layer of a Solution $(\text{CuSO}_4 + 1080 \text{ NH}_3)/90$ (Normal). Intensity of light: $0.2364 \text{ cal/cm}^2/\text{sec}$. The measuring instrument: Quadrant electrometer.

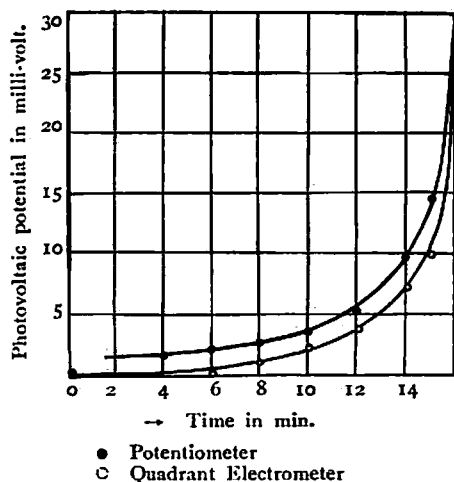


Fig. 1.

The Influence of the Measuring Instrument on the Photovoltaic Potential.

As is seen, variation in the measuring instruments used gives rise to slight variation in photovoltaic potentials for the same intensity of light. This may be because some electric current is taken out in the case of a potentiometer. Even in this case, however, the difference was limited within 1% in such a degree of light intensity. Accordingly, a potentiometer was used in the present experiment.

Expt. II. Intensity of Light and Change of Photovoltaic Potential with Time.

The change of the photovoltaic potential was measured with a monochromatic light of $492\mu\mu$ and three kinds of intensities of light—0.004054, 0.02843, and 5.575 cal/cm²/sec. The results obtained are given in Table II, a, b, c, and Fig. II.

Table II. a.

The Change of Velocity in the Photochemical Reaction with Intensity of Light at $25\pm 0.02^\circ\text{C}$.

Time (mins).	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \text{H}_2$) (volts)	Po ₂ (oxygen-pressure) (atm)
Exposure				
0	0.2322	0	0.8425	1.000×10^{-26}
1	0.2734	41.2	0.8837	0.581×10^{-23}
2	0.2767	44.5	0.8870	0.981 "
3	0.2783	46.1	0.8886	1.293 "
5	0.2799	47.7	0.8902	1.652 "
6	0.2803	48.1	0.8906	1.773 "
9	0.2805	48.3	0.8908	1.994 "
10	0.2809	48.7	0.8912	2.041 "
14	0.2809	48.7	0.8912	2.041 "
20	0.2809	48.7	0.8912	2.041 "
24	0.2809	48.7	0.8912	2.041 "
30	0.2809	48.7	0.8912	2.041 "
Light off				
0	0.2809	48.7	0.8912	2.041×10^{-23}
3	0.2740	41.8	0.8855	8.128×10^{-24}
5	0.2697	37.5	0.8812	4.266 "
7	0.2668	34.6	0.8783	2.692 "
8.5	0.2635	31.3	0.8750	1.585 "
11	0.2593	27.1	0.8708	8.511×10^{-25}
12	0.2573	25.0	0.8687	5.888 "
13.5	0.2539	21.7	0.8654	3.548 "
15	0.2509	18.7	0.8624	2.239 "
18	0.2457	13.5	0.8572	1.000 "
20	0.2444	12.2	0.8559	8.128×10^{-26}

$25^\circ \pm 0.02^\circ\text{C}$. Light source: a 100V-1000W Tungsten-filament lamp, operating from a battery supply. The light monochromatic($492\mu\mu$) was passed through a Wratten light filter. Intensity of light: 5.575 cal/cm²/sec. The measuring instrument: Potentiometer.

Table II, b.

The Change of Velocity in the Photochemical Reaction with Intensity of Light at $25^{\circ} \pm 0.02^{\circ} \text{C}$.

Time (mins)	EM.F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \text{I}_2$) (volts)	Po ₂ (oxygen-pressure) (atm)
Exposure				
0	0.2322	0	0.8425	1.000×10^{-26}
1	0.2412	9.0	0.8515	4.169 "
2	0.2450	12.8	0.8553	7.418 "
4	0.2464	14.2	0.8567	9.120 "
6	0.2471	14.9	0.8574	1.023×10^{-25}
8	0.2476	15.4	0.8579	1.096 "
10	0.2478	15.6	0.8581	1.148 "
12	0.2477	15.5	0.8580	1.122 "
14	0.2478	15.6	0.8581	1.148 "
20	0.2478	15.6	0.8581	1.148 "
24	0.2478	15.6	0.8581	1.148 "
30	0.2478	15.6	0.8581	1.148 "
Light off				
0	0.2478	15.6	0.8581	1.148×10^{-25}
2	0.2449	12.7	0.8544	6.310×10^{-26}
3	0.2422	10.0	0.8525	4.784 "
4	0.2412	9.0	0.8515	4.074 "
5	0.2401	7.9	0.8504	3.467 "
6	0.2390	6.8	0.8493	2.884 "
7	0.2374	5.2	0.8477	2.291 "
8.5	0.2360	3.8	0.8463	1.950 "
10	0.2354	3.2	0.8457	1.660 "

$25^{\circ} \pm 0.02^{\circ} \text{C}$. Light source: a 100V—1000W Tungsten-filament lamp, operating from a battery supply. The light monochromatic ($492 \mu\mu$) was passed through a Wratten light filter. Intensity of light: $0.02843 \text{ cal/cm}^2/\text{sec}$.

Table II, c.

The Change of Velocity in the Photochemical Reaction with Intensity of Light at $25^{\circ} \pm 0.02^{\circ} \text{C}$.

Time (mins.)	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E.M.F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \text{I}_2$) (volts)	Po ₂ (oxygen-pressure) (atm)
Exposure				
0	0.2324	0	0.8423	9.729×10^{-27}
1	0.2355	3.1	0.8454	1.570×10^{-26}
2	0.2362	3.8	0.8461	1.754 "
3	0.2368	4.4	0.8467	1.941 "
4	0.2373	4.9	0.8472	2.089 "
5	0.2376	5.2	0.8475	2.168 "
6	0.2379	5.5	0.8478	2.249 "
7	0.2381	5.7	0.8480	2.355 "
8	0.2382	5.8	0.8481	2.399 "
9	0.2383	5.9	0.8482	2.443 "
10	0.2383	5.9	0.8482	2.443 "
11	0.2383	5.9	0.8482	2.443 "
12	0.2383	5.9	0.8482	2.443 "
30	0.2383	5.9	0.8482	2.443 "
Light off				
0	0.2383	5.9	0.8482	2.443×10^{-26}
1	0.2373	4.9	0.8472	2.022 "
2	0.2362	3.8	0.8461	1.723 "
3.5	0.2352	2.8	0.8451	1.503 "
4	0.2346	2.2	0.8445	1.373 "
5	0.2342	1.8	0.8441	1.273 "
6	0.2338	1.4	0.8437	1.213 "
7	0.2335	1.1	0.8434	1.153 "
8	0.2333	0.9	0.8432	1.123 "

$25^{\circ} \pm 0.02^{\circ} \text{C}$. Light source: a 100V—100W Tungsten-filament lamp, operating from a battery supply. The monochromatic light ($492 \mu\mu$) was passed through a Wratten light filter. Intensity of light: $0.004055 \text{ cal/cm}^2/\text{sec}$.

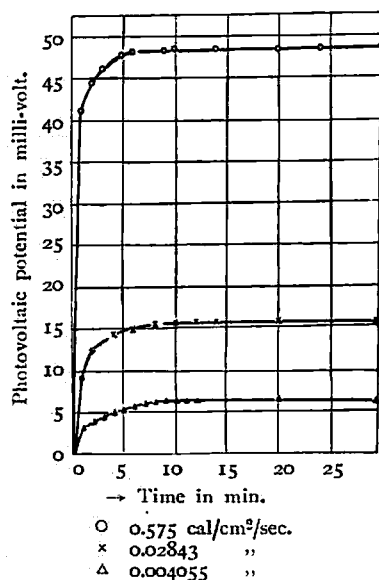


Fig. II

The Change of Velocity in the Photochemical Reaction with Intensity of Light at $25^{\circ} \pm 0.02^{\circ}\text{C}$.

The experimental results show that the time taken before the equilibrium of the Becquerel effect is established is not influenced by the intensity of light and the three equilibrium photovoltaic potential is proportional to light. It is also shown that the reaction velocity after the exposure increases in proportion to light intensity.

Expt. III. Wave Length and Change of Photo-electrode with Time.

The effect of wave length upon the change of the photovoltaic potential was examined. The change of the photovoltaic potential with time was measured with a given intensity of such monochromatic lights as $430\text{ }\mu\mu$ (violet), $492\text{ }\mu\mu$ (green), $550\text{ }\mu\mu$ (yellow), and $640\text{ }\mu\mu$ (red). The results are given in Table III a, b, c, d, and in Fig. III.

Table III, a.

The Change of Velocity in the Photochemical Reaction with Wave Length of Light at 25°C .

Time (mins.)	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO}, \frac{\text{N}}{10}\text{NaOH} \text{H}_2$) (volts)	P_{O_2} (oxygen-pressure) (atm)
Exposure				
0	0.2324	0	0.8423	9.727×10^{-27}
1	0.2349	2.5	0.8449	1.432×10^{-26}
2	0.2359	3.5	0.8458	1.675 "
3	0.2364	4.0	0.8463	1.803 "
4	0.2368	4.4	0.8467	1.905 "
5	0.2371	4.7	0.8470	2.014 "
6	0.2373	4.9	0.8472	2.089 "
7	0.2376	5.2	0.8475	2.168 "
8	0.2377	5.3	0.8476	2.228 "
9	0.2379	5.5	0.8478	2.291 "
10	0.2379	5.5	0.8478	2.291 "
11	0.2379	5.5	0.8478	2.291 "
12	0.2379	5.5	0.8478	2.291 "
Light off				
0	0.2379	5.5	0.8478	2.291×10^{-26}
1.2	0.2364	4.0	0.8463	1.803 "
3	0.2352	2.8	0.8451	1.500 "
4	0.2348	2.4	0.8447	1.393 "
5	0.2343	1.9	0.8442	1.294 "
5.5	0.2340	1.6	0.8439	1.236 "
6.5	0.2338	1.4	0.8437	1.159 "
7.5	0.2334	1.0	0.8433	1.133 "
8	0.2333	0.9	0.8432	1.107 "
8.5	0.2331	0.7	0.8430	1.086 "

$25^{\circ} \pm 0.02^{\circ}\text{C}$. Light source: a 100V—200W Tungsten-filament lamp, operating from a battery supply. The monochromatic light ($550\text{ }\mu\mu$) was passed through a Wratten light filter. Intensity of light: $0.004055\text{ cal/cm}^2\text{/sec}$.

Table III, b.

The Change of Velocity in the Photochemical Reaction with Wave Length of Light at 25°C.

Time (mins.)	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO}, \frac{\text{N}}{10}\text{NaOH} \text{H}_2$) (volts)	Po ₂ (oxygen-pressure) (atm)
Exposure				
0	0.2324	0	0.8423	9.729×10^{-27}
1	0.2355	3.1	0.8454	1.570×10^{-26}
2	0.2362	3.8	0.8461	1.754 "
3	0.2368	4.4	0.8467	1.941 "
4	0.2373	4.9	0.8472	2.089 "
5	0.2376	5.2	0.8475	2.168 "
6	0.2379	5.5	0.8478	2.249 "
7	0.2381	5.7	0.8480	2.355 "
8	0.2382	5.8	0.8481	2.399 "
9	0.2383	5.9	0.8482	2.443 "
10	0.2383	5.9	0.8482	2.443 "
11	0.2383	5.9	0.8482	2.443 "
12	0.2383	5.9	0.8482	2.443 "
30	0.2383	5.9	0.8482	2.443 "
Light off				
0	0.2383	5.9	0.8482	2.443×10^{-26}
1	0.2373	4.9	0.8472	2.022 "
2	0.2362	3.8	0.8461	1.723 "
3	0.2352	2.8	0.8451	1.503 "
4	0.2346	2.2	0.8445	1.373 "
5	0.2342	1.8	0.8441	1.273 "
6	0.2338	1.4	0.8437	1.213 "
7	0.2335	1.1	0.8434	1.153 "
8	0.2333	0.9	0.8432	1.123 "

25°±0.02°C. Light source: a 100V—200W Tungsten-filament lamp, operating from a battery supply. The monochromatic light (492 μ) was passed through a Wratten light filter. Intensity of light: 0.004055 cal/cm²/sec.

Table III, c.

The Change of Velocity in the Photochemical Reaction with Wave Length of Light at 25°C.

Time (mins.)	E. M. F. of Cell [A] (volts)	Photovoltaic Potential (milli-volts)	Ea (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO}, \frac{\text{N}}{10}\text{NaOH} \text{H}_2$) (volts)	Po ₂ (oxygen-pressure) (atm)
Exposure				
0	0.2324	0	0.8423	9.727×10^{-27}
1	0.2346	2.2	0.8445	1.387×10^{-26}
2	0.2352	2.8	0.8451	1.500 "
3	0.2357	3.3	0.8456	1.614 "
4	0.2360	3.6	0.8459	1.694 "
5	0.2362	3.8	0.8461	1.754 "
6	0.2365	4.1	0.8464	1.820 "
7	0.2366	4.2	0.8465	1.854 "
8	0.2367	4.3	0.8466	1.892 "
9	0.2368	4.4	0.8467	1.923 "
10	0.2368	4.4	0.8467	1.923 "
11	0.2368	4.4	0.8467	1.923 "
12	0.2368	4.4	0.8467	1.923 "
Light off				
0	0.2368	4.4	0.8467	1.923
1.5	0.2338	3.4	0.8457	1.660
2.5	0.2350	2.6	0.8449	1.445
3.5	0.2345	2.1	0.8444	1.330
4	0.2341	1.7	0.8440	1.259
5	0.2338	1.4	0.8437	1.202
6.5	0.2334	1.0	0.8433	1.127
7.5	0.2331	0.7	0.8430	1.076


25°±0.02°C. Light source: a 100V—200W Tungsten-filament lamp, operating from a battery supply. The monochromatic light (430 μ) was passed through a Wratten light filter. Intensity of light: 0.004055 cal/cm²/sec.

Table III, d.

The Change of Velocity in the Photochemical Reaction with Wave Length of Light at 25°C.

Time (mins.)	E. M. F. of Cell [A] (volts.)	Photovoltaic Potential (milli-volts.)	E_a (E. M. F. of $\text{Cu} \text{Cu}_2\text{O}, \text{CuO}, \frac{\text{N}}{10}\text{NaOH} \text{H}_2$) (volts)	P_{O_2} (oxygen-pressure) (atm)
Exposure				
0	0.2324	0	0.8423	9.727×10^{-27}
1	0.2343	1.9	0.8442	1.306×10^{-26}
2	0.2350	2.6	0.8449	1.459 "
3	0.2354	3.0	0.8453	1.542 "
4	0.2357	3.3	0.8456	1.570 "
5	0.2360	3.6	0.8459	1.670 "
6	0.2361	3.7	0.8460	1.722 "
7	0.2362	3.8	0.8461	1.745 "
8	0.2363	3.9	0.8462	1.786 "
9	0.2363	3.9	0.8462	1.786 "
10	0.2363	3.9	0.8462	1.786 "
11	0.2363	3.9	0.8462	1.786 "
12	0.2363	3.9	0.8462	1.786 "
Light off				
0	0.2363	3.9	0.8462	1.786×10^{-26}
1.2	0.2354	3.0	0.8453	1.542 "
2.5	0.2347	2.3	0.8446	1.328 "
3	0.2343	1.9	0.8442	1.294 "
4	0.2339	1.5	0.8438	1.225 "
5	0.2334	1.0	0.8433	1.138 "
6	0.2332	0.8	0.8431	1.096 "
7.5	0.2330	0.6	0.8429	1.057 "

25° ± 0.02°C. Light source: a 100V—200W Tungsten-filament lamp, operating from a battery supply. The monochromatic light (640μμ) was passed through a Wratten light filter. Intensity of light: 0.004055 cal/cm²/sec.

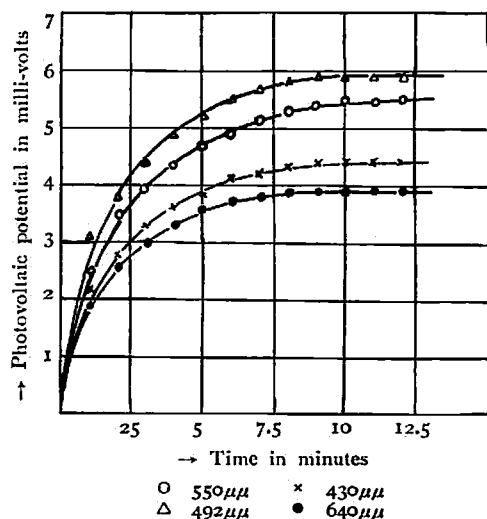

The Change of Velocity in the Photochemical Reaction with Wave Length of Light at 25°C.

It is apparent from these that the time elapsing before the equilibrium of the Becquerel effect is established is almost uniform, regardless of the wave-length, and that variation in the wave-length gives rise to variation in the photo-effect.

Expt. IV. Wave Length and Maximum Photovoltaic Potential.

The relation between the wave length and the maximum photovoltaic potential was examined. The examination was made with three electrodes—No. 1, No. 2 and No. 3. The copper

oxide electrodes which had been in equilibrium in the dark were exposed to six kinds of monochromatic lights, and their maximum photovoltaic potentials measured. During the experiment the electric current and voltage were regulated by means

of a thermopile so that the intensity of light might be kept constant. The experimental results are given in Table IV and Fig. IV, which show that the

Table IV.
The Influence of the Wave Length of Light on the Maximum Photovoltaic Potential

Monochromatic Light ($\mu\mu$)	Number of Cell.	I _{Fe} . Maximum Photovoltaic Potential (volts)	II _{Fe} . Maximum Photovoltaic Potential (volts)	III _{Fe} . Maximum Photovoltaic Potential (volts)	Mean. (volts)
U. V. 380		0.0035	0.0036	0.0036	0.0036
Violet 430		0.0044	0.0043	0.0043	0.0043
Green 492		0.0058	0.0058	0.0058	0.0058
Yellow 550		0.0055	0.0056	0.0055	0.0055
Red 640		0.0039	0.0040	0.0039	0.0039
I. R. 810		0.0030	0.0031	0.0031	0.0031

25°±0.02°C. Light source: a 100V—500W Tungsten-filament lamp, operating from a battery supply. The monochromatic lights, 380, 492, 550, 640 and 810 $\mu\mu$, were passed through a Wratten light filter. Intensity of light: 0.004055 cal/cm²/sec.

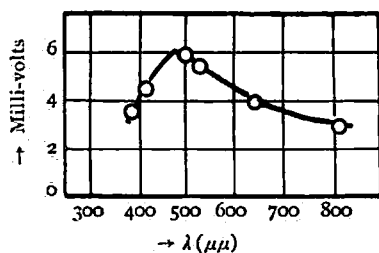


Fig. IV

The Influence of the Wave Length of Light on the Maximum Photovoltaic Potential (Intensity of Light: 0.004055 cal/cm²/sec. 25°±0.02°C.)

photovoltaic potential of $\text{Cu} \mid \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10}$ NaOH has a selective effect on different wave lengths of light, and that its maximum photo-effect lies between 450–500 $\mu\mu$.

Expt. V. Intensity of Light and Saturated Maximum Photovoltaic Potential.

An electrode, $\text{Cu} \mid \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10}$ NaOH, which had been in equilibrium in the dark,

Table V.
The Influence of Intensity of Light on the Maximum Photovoltaic Potential

Intensity of light (cal/cm ² /sec.)	E. M. F. of Cell [A] (obs.)	E _a (E. M. F. of $\text{Cu} \mid \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \mid \text{H}_2$) (calc.)	Maximum Photovoltaic Potential
0	0.2323 volt	0.8424 volt	—
0.002318	0.2298	0.8449	+0.0025
0.004055	0.2282	0.8465	+0.0041
0.008130	0.2233	0.8514	+0.0090
0.02843	0.2174	0.8573	+0.0149
0.1042	0.2087	0.8660	+0.0236
5.575	0.1848	0.8899	+0.0475
14.100	0.1628	0.9119	+0.0695

25°±0.02°C. Light source; a 100V—1000W Tungsten-filament lamp, operating from a battery supply. The monochromatic light (492 $\mu\mu$) was passed through a Wratten light filter.

- 5) Photochemical equilibria corresponding to intensities of light can be established. The photovoltaic potential in equilibrium will be called the maximum photovoltaic potential for convenience' sake.

was exposed to light of various intensities and its saturated maximum photovoltaic potentials were measured. The results are given in Table V and Fig. V.

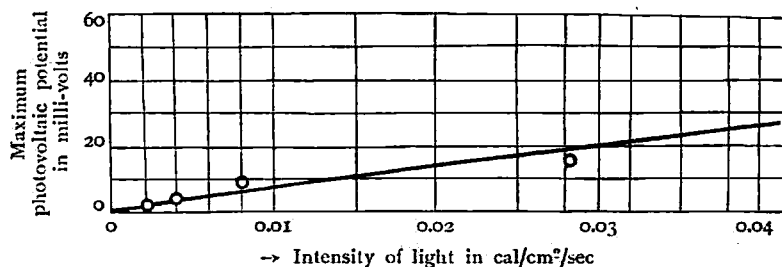


Fig. V.

The Influence of the Intensity of Light on the Maximum Photovoltaic Potential.

Expt. VI. Temperature and Change of Photovoltaic Potential.

The influence of temperature on the photovoltaic potential was examined with the copper oxide electrodes which reached equilibrium at 0°, 10°, 25°, 35° and 45°C. respectively. The results are given in Table VI and Fig. VI.

Table VI.

The Influence of Temperature on the Maximum Photovoltaic Potential

Intensity of light (cal/cm ² /sec.)	0		0.002318		0.004055		0.00818	
	E _{at} & ΔE _t (milli-volts)		E	ΔE	E	ΔE	E	ΔE
Temp. °C								
0	855.07	—	857.32	—	859.00	—	863.85	—
18	845.99	9.12	848.37	8.95	850.00	9.00	856.87	8.98
25	842.40	12.67	844.90	12.42	846.50	12.50	851.40	12.45
35	837.32	17.75	838.92	17.40	841.50	17.50	846.41	17.44
45	832.27	22.80	834.97	22.35	836.40	22.50	841.45	22.40
$-\frac{\Delta E}{\Delta T}$ (mean)		5.07		4.97		5.00		4.98

Intensity of light (cal/cm ² /sec.)	0.02843		0.1042		5.575		14.100	
	E _{at} & ΔE _t (milli-volts)		E	ΔE	E	ΔE	E	ΔE
Temp. °C								
0	869.80	—	878.50	—	902.27	—	924.20	—
18	860.80	9.00	869.50	9.00	893.37	8.90	915.36	8.84
25	857.30	12.50	866.00	12.50	889.90	12.37	911.90	12.30
35	852.28	17.52	861.15	17.50	884.92	17.35	907.00	17.20
45	847.34	22.51	856.15	22.50	879.97	22.30	902.10	22.10
$-\frac{\Delta E}{\Delta T}$ (mean)		5.01		5.00		4.95		4.92

Light source: a 100V—1000V Tungsten-filament lamp, operating from a battery supply. The monochromatic light (492 μ) was passed through a Wratten light filter.

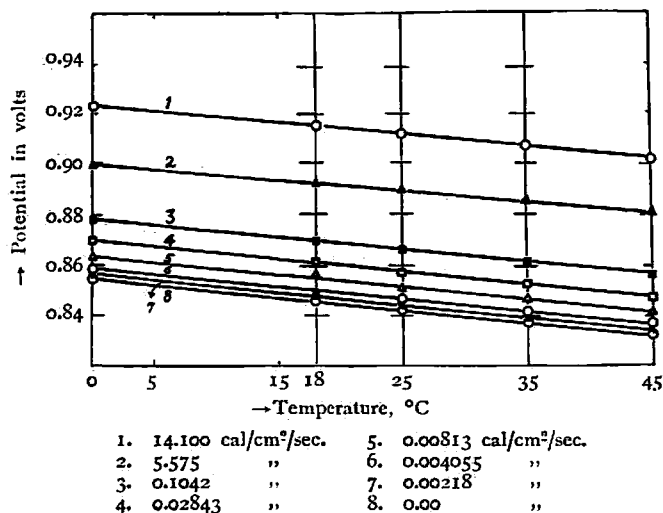


Fig. VI.

The Influence of Temperature on the Maximum Photovoltaic Potential.

As is seen, the photo-electrode potential which is in equilibrium in the dark decreases with the increase of temperature.

The photovoltaic potential for the the same intensity of light is not correlated to the rise of temperature. Therefore the temperature coefficients of voltage are equal both in the dark and in the light.

Theoretical.


1) Consideration from the Standpoint of the Reaction Kinetics.

1) Copper Oxide Electrode as a Reaction System.

An electrode, $\text{Cu} \mid \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH}$, which has reached equilibrium in the dark is expressed as a heterogeneous reversible reaction thus,



When this system is exposed to light, it reaches photochemical equilibrium according to a reaction,

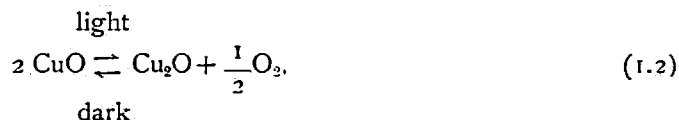

as already said in the preceding report. It is apparent from the experimental results that when light is shut off the reaction proceeds to the direction indicated

by \leftarrow , and equilibrium is restored in the dark. As far as this photochemical reaction velocity is concerned, it is clear that the reaction must be treated as a reversible reaction. The question whether the reverse reaction is affected by light or not has not been solved yet, and so the author intends to make discussion under the assumption that the reverse reaction has no influence upon light, and if it has any influence, further consideration will have to be made.

In equation (1.2), supposing that the density of the solids is constant, the following velocity equation is assumed:

$$\frac{d\Delta p}{dt} = k_1 \cdot J_{\text{abs}} - k_d' \cdot [O_2], \quad (1.3)$$

where P is the oxygen pressure during exposure, k , and kd' the reaction velocity constants in the light and the dark respectively, and J_{abs} the intensity of light.

First we shall calculate the velocity from this equation. The relation is

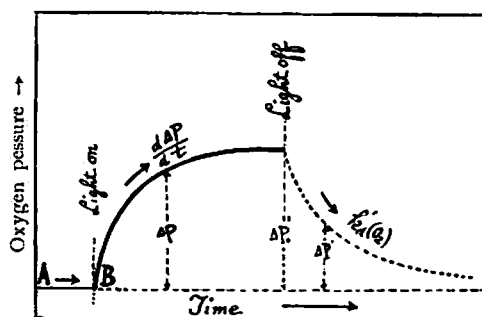


Fig. 7

graphically shown in Fig. VII, in which the height of A shows the equilibrium pressure of oxygen in the dark.

2) Photovoltaic Potential.

Before the calculation of $\frac{d\Delta p}{dt}$ from equation (1.3) it is necessary to make clear the photovoltaic potential. As has been mentioned in the preceding

report, when the copper oxide electrode was combined with hydrogen electrode, an oxy-hydrogen cell was formed. Therefore E. M. F. can be obtained from the following equation:

$$E_a = E_p + \frac{0.059}{4} \log P_{O_2}, \quad (1.4)$$

at $25 \pm 0.02^\circ\text{C}$. Here,

$$E_a: \text{E. M. F. of } \text{Cu} \left| \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \right| \text{H}_2 \text{ (at } 25^\circ\text{C.)}$$

(x atm) (1 atm)

$$E_p: \text{E. M. F. of } \text{O}_2 \left| \frac{\text{N}}{10} \text{NaOH} \right| \text{H}_2 \text{ (at } 25^\circ\text{C.)}$$

(1 atm) (1 atm)

Putting $E_p = a$ and $\frac{0.059}{4} = b$, we have

$$E_a = a + b \log P_{O_2}. \quad (1.5)$$

The photovoltaic potential ΔE_a is determined by the difference between the

potential in the light, E_a' , and that in the dark, E_a ; hence

$$\begin{aligned} \text{(dark)} \quad E_a &= a + b \log P_{O_2} \\ \text{(light)} \quad E_a' &= a + b \log P_{O_2}' \\ \therefore E_a' - E_a &= b (\log P_{O_2}' - \log P_{O_2}) \end{aligned} \quad (1.6)$$

$$\log \frac{P_{O_2}'}{P_{O_2}} = \frac{E_a' - E_a}{b} = \frac{\Delta E_a}{b}$$

$$\Delta E_a = b \log \frac{P_{O_2}'}{P_{O_2}}$$

$$\frac{P_{O_2}'}{P_{O_2}} 10^{\frac{E_a' - E_a}{b}} \quad \text{or} \quad \frac{P_{O_2}'}{P_{O_2}} - 1 = 10^{\frac{E_a' - E_a}{b}} - 1$$

$$\therefore \frac{P_{O_2}' - P_{O_2}}{P_{O_2}} = 10^{\frac{E_a' - E_a}{b}} - 1.$$

$$\Delta P = P_{O_2} \left\{ 10^{\frac{E_a' - E_a}{b}} - 1 \right\}, \dots \dots \dots (\text{at } 25^\circ\text{C.}) \quad (1.7)$$

where P_{O_2} is the equilibrium oxygen pressure of the electrode in the dark. The electrode oxygen pressure Δp equivalent to the photovoltaic potential $\Delta E_a = E_a$ can be calculated from the equation.

3) Reaction Velocity after Shutting off Light.

When light was shut off, equation (1.2), the equilibrium system during exposure, proceeded to the direction indicated by \leftarrow . This is the case where $K_1 \cdot J_{abs} = 0$ in equation (1.3), and it may be rewritten as follows:

$$-\frac{d(\Delta P')}{dt} = k_d' [O_2], \quad (1.8)$$

where $\Delta P'$ is the difference of the pressure of oxygen after shutting off light,

$$\text{or} \quad -\ln \Delta P = k_d' t + C. \quad (1.9)$$

In equation (1.9), if $t=0$, that is, the value of $\Delta P'$ at the instant of shutting off light is taken to be $\Delta P_0'$, we have

$$C = -\ln \Delta P_0', \quad (1.10)$$

$$\therefore -2.303 \log \frac{\Delta P_0'}{\Delta P'} = k_d' t. \quad (1.11)$$

In order to see if this equation gives the observed values of the curve of oxygen pressure decrease, the author calculated k_d' through equation (1.11) from several points on the curves of the oxygen pressure decrease obtained by Expts. II and III, and obtained 0.306 as the mean value, which proved to be a constant in each case. As one of those examples Expt. II, c is given in Table VII and graphically in Fig. VIII.

Table VII.
 k_d' : velocity constant of the dark reaction.

Time (mins.)	$\Delta P'$ (atm) (obs.)	k_d'	$\Delta P'$ (atm) (calc.)
0	1.47×10^{-26}	—	1.470×10^{-26}
1	1.05 "	0.314	1.053 "
2	0.75 "	0.324	0.775 "
3	0.53 "	0.331	0.571 "
4	0.40 "	0.319	0.420 "
5	0.30 "	0.313	0.309 "
6	0.24 "	0.298	0.228 "
7	0.18 "	0.296	0.168 "
8	0.15 "	0.275	0.123 "
		mean 0.308	

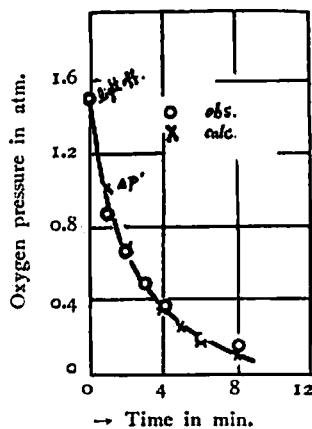


Fig. 8

The relation between the velocity constants of the reaction in the dark and the intensity of light is given in Table VIII, and that between the constants and the wave length in Table IX. As is seen in these tables, both the mean values are precisely 0.306. This shows that the velocity constants after the shutting off of light is fairly constant in each case, regardless of the intensity of light and wave length. P' was calculated from this mean value and Fig. VIII shows that it is in good agreement with the observed value $\Delta P'$.

Table VIII.
 k_d' : velocity constant of the dark reaction.


Wave length (μ)	$J_{\text{abs.}}$ The light energy absorbed, before light off. (cal/cm ² /sec.)	k_d' (atm/sec)	mean. (atm/sec)
492	5.575	0.300	0.306
492	0.02843	0.302	
492	0.004055	0.316	

Table IX.
 k_d' : velocity constant of the dark reaction.

Wave length (μ)	$J_{\text{abs.}}$	k_d'	mean.
430	0.004055	0.303	0.306
492	"	0.316	
550	"	0.291	
640	"	0.315	

4) Reaction Velocity after Exposure.

A) Calculation of the Reaction Velocity during Exposure. When the copper oxide electrode which had been in equilibrium in the dark was exposed to light, a photochemical reversible reactions:



took place and from this chemical relation the velocity equation (1.3) was assumed. (See Theoretical, 1.)

In this expression, $k_1 \cdot J_{abs}$, the first term in the side, is a constant for a given intensity of light, according to the author's assumptions.

When the reaction system reached a stationary state during the course of exposure,

$$\frac{d\Delta P}{dt} = 0.$$

Therefore,

$$k_1 \cdot J_{abs} = k'_2 [O_2], \quad (1.12)$$

the right side of which can be obtained from the observed value, because the mean value of the reaction velocity constant, k'_2 , is already given as 0.306, and the value of O_2 which is the oxygen pressure equivalent to the photovoltaic potential is calculated from the observed value at the time when the system has reached a stationary state. Accordingly, $k_1 \cdot J_{abs}$ can be easily calculated from equation (1.12); the values obtained are given in Table X.

Table X.
 $k_1 J_{abs}$: specific constant of the light reaction at 25°C.

Wave length ($\mu\mu$)	J_{abs} The light energy absorbed (cal/cm ² /sec)	Oxygen pressure in equilibrium (atm/min)	$k_1 J_{abs}$ (atm/min)
492	5.575	2.04×10^{-23}	0.623×10^{-23}
492	0.02843	1.028×10^{-25}	0.317×10^{-25}
492	0.004055	1.470×10^{-26}	0.452×10^{-26}
430	0.004055	0.950×10^{-25}	0.292×10^{-26}
492	0.004055	1.470 "	0.452 "
550	0.004055	1.318 "	0.404 "
640	0.004055	0.813 "	0.250 "

The values of k_1 for variation in the wave length and intensity of light are given in Table XI, a, and b.

Table XI, a.
 k_1 : velocity constant of the light reaction at 25°C.

Wave length ($\mu\mu$)	J_{abs} The light energy absorbed (cal/cm ² /sec)	k_1 (atm/sec)
492	0.004055	1.86×10^{-26}
492	0.02843	1.85×10^{-26}
492	5.575	1.88×10^{-26}
		mean 1.863×10^{-26}

Table XI, b.

 k_1 : velocity constant of the light reaction at 25°C.

Wave length (μ)	The light energy absorbed ($\text{cal/cm}^2/\text{sec}$)	k_1 (atm/sec)
430	0.004055	0.120×10^{-26}
492	0.004055	0.186 "
550	0.004055	0.166 "
640	0.004055	0.103 "

This shows that k_1 which is the so-called photochemical velocity constant, is constant regardless of the intensity of light, and has a selective effect on the change of wave length, its maximum value being between 400 μ and 500 μ .

(B) The Reaction Velocity during Exposure, $\frac{d\Delta P}{dt}$. As above said, from the values of k_1 , J_{abs} and kd' and equation (1.7), the reaction velocity $\frac{d\Delta P}{dt}$ can be easily calculated. As one of the examples, Expt. III, c is shown in Table XII, where the calculated values agree quite well with the observed ones. This justifies equation (1.2) proposed by the author.

Table XII.

t (minutes)	ΔP ($10^{-26}\text{atm}/\text{min}$)	$kd'(\Delta P)=kd'[\text{O}_2]$ ($10^{-26}\text{atm}/\text{min}$)	$k_1 \cdot J_{abs}$ ($10^{-26}\text{atm}/\text{min}$)	$\frac{d\Delta P}{dt}$ ($10^{-26}\text{atm}/\text{min}$) (calc.)	$\frac{d\Delta P}{dt}$ ($10^{-26}\text{atm}/\text{min}$) (obs.)
0	0	—	—	—	—
1	0.414	0.127	0.292	0.165	0.124
2	0.527	0.162	0.292	0.130	0.111
3	0.641	0.197	0.292	0.095	0.095
4	0.721	0.221	0.292	0.071	0.076
5	0.781	0.240	0.292	0.050	0.060
6	0.847	0.260	0.292	0.032	0.049
7	0.881	0.271	0.292	0.021	0.039
8	0.919	0.282	0.292	0.010	0.032
9	0.950	0.292	0.292	0	0.019
10	0.950	0.292	0.292	0	0
11	0.950	0.292	0.292	0	0
12	0.950	0.292	0.292	0	0

5) Photochemical Reaction Velocity, Light Intensity, and Wave Length.

In the preceding section the reaction velocity equation (1.3) was experimentally-proved. Accordingly, the pure photochemical reaction excluding the dark reaction is apparently of the zero order from equation (1.3):

$$\frac{dP}{dt} k_1 \cdot J_{abs} = k_1' \quad (1.13)$$

where K_1 is a particular constant including the intensity of light, P , the oxygen pressure equivalent to

$$P = \Delta P + \Delta p \quad (1.14)$$

as is shown in Fig. IX.

Hence

$$\begin{aligned} P &= k_1 \cdot J_{abs} \cdot t \\ &= k_1' \cdot t \end{aligned} \quad (1.15)$$

The values obtained are given in Table XIII and XIV, and graphically in Figs. X and XI, which prove that the photochemical reaction is of the zero order, and also show that the stronger the intensity of light the

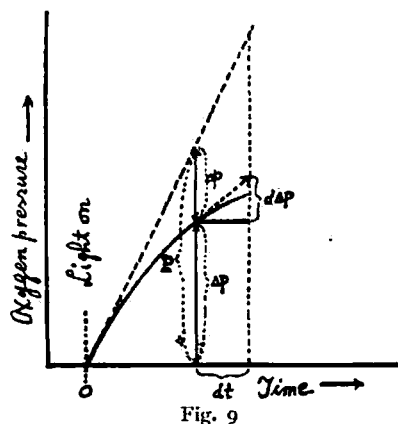


Table XIII.

Time (mins.)	Wave length ($\mu\mu$)	P (atm)		
		$J=5.575$ cal/cm ² /sec	$J=0.02843$ cal/cm ² /sec	$J=0.004055$ cal/cm ² /sec
0	492	0	0	0
1	492	0.623×10^{-23}	0.317×10^{-25}	0.452×10^{-26}
2	492	1.246 "	0.634 "	0.904 "
3	492	—	—	1.356 "
4	492	2.492 "	1.268 "	1.808 "
5	492	—	—	2.260 "
6	492	3.738 "	1.902 "	2.712 "
7	492	—	—	3.164 "
8	492	4.984 "	2.536 "	3.616 "
9	492	—	—	4.068 "
10	462	6.230 "	3.170 "	4.520 "
20	492	12.460	6.340 "	9.040 "

Table XIV.

Time (mins.)	Intensity of light (cal/cm ² /sec)	P (atm)			
		w. l.=430 $\mu\mu$	w. l.=492 $\mu\mu$	w. l.=550 $\mu\mu$	w. l.=640 $\mu\mu$
0	0.004055	0	0	0	0
1	0.004055	0.292×10^{-26}	0.452×10^{-26}	0.405×10^{-26}	0.250×10^{-26}
2	0.004055	0.584 "	0.904 "	0.810 "	0.500 "
3	0.004055	0.876 "	1.356 "	1.215 "	0.750 "
4	0.004055	1.168 "	1.808 "	1.620 "	1.000 "
5	0.004055	1.460 "	2.260 "	2.025 "	1.250 "
6	0.004055	1.752 "	2.712 "	2.430 "	1.500 "
7	0.004055	2.044 "	3.164 "	2.835 "	1.750 "
8	0.004055	2.336 "	3.616 "	3.240 "	2.000 "
9	0.004055	2.628 "	4.068 "	3.645 "	2.250 "
10	0.004055	2.920 "	4.520 "	4.050 "	2.500 "
20	0.004055	5.840 "	9.040 "	8.100 "	5.000 "

greater becomes the reaction velocity and it reaches a maximum for a particular wave length.

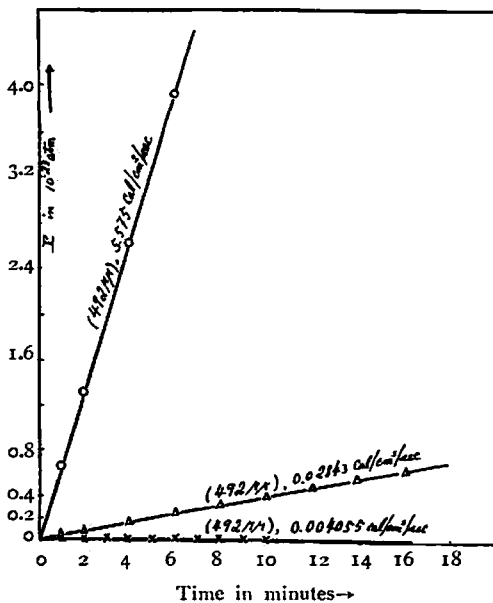


Fig. 10

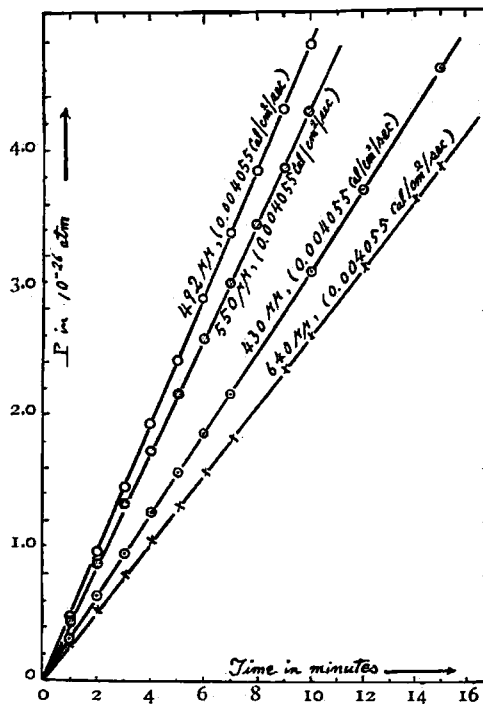


Fig. 11

5) Examination of the Absolute Value of Equilibrium Hydrogen Pressure of the Cell.

The equilibrium pressure of the copper oxide electrode was measured by Nernst's formula as copper electrode, and $4\text{CuO} \rightleftharpoons 2\text{Cu}_2\text{O} + \text{O}_2$ was proposed as the mechanism of the photo-cell used. From this reaction mechanism, the author tried to confirm theoretical consideration of the reaction velocity from the standpoint of the ordinary reaction kinetics, and found that the theoretical consideration agreed quite well with the experimental as already mentioned.

Whether the ordinary reaction kinetics is applicable to the experiments carried out in such a degree of the pressure of hydrogen as 10^{-26} atm is a question, but further investigation will solve it⁶⁾. There is, however, no question about the applicability from the formal view-point of the reaction kinetics.

6) According to the kinetical theory of gas, the number of the molecules colliding with 1 cm^2 of the surface area for 1 minute is given by

$$n = 1^2 \times v \times n_0,$$

II) Thermodynamical Consideration.

In order to make clear the thermodynamical property of the cell used, the following measurements were made: (i) the calculation of ΔF and ΔH in the light and the dark of a reversible reaction system, $Cu_2O + \frac{1}{2} O_2 = 2 CuO$, (ii) that of equilibrium constant K of the same system, and (iii) that of the entropy of CuO .

i) ΔF and ΔH in the Light and the Dark of a Heterogeneous System, $Cu_2O + \frac{1}{2} O_2 = 2 CuO$.

From E. M. F. ($=0.8424$,⁷⁾) of $Cu | Cu_2O, CuO \frac{N}{10} NaOH | H_2$ at $25^\circ \pm 0.02^\circ C$., we have

$$2 CuO + H_2 = Cu_2O + H_2O$$

$$(\Delta F)_{298}^D = -2 \times 23,074 \times 0.8424 = -38,875 \text{ cal.} \quad (2.1)$$

$$(\Delta H)_{298}^D = -2 \times 23,074 \times (0.000507 \times 298.1 + 0.8424)$$

$$= -45,830 \text{ cal.} \quad (2.2)$$

In the case of the formation of water,

$$H_2 + \frac{1}{2} O_2 = H_2O$$

$$(\Delta F)_{298}^D = -56,560^8)$$

$$(\Delta H)_{298}^D = -68,270^9)$$

Hence,

$$Cu_2O + \frac{1}{2} O_2 = 2 CuO$$

$$(\Delta F)_{298}^D = -17,620 \text{ cal.} \quad (2.5)$$

$$(\Delta H)_{298}^D = -22,440 \text{ cal.} \quad (2.6)$$

There is no experimental result appropriate to compare with this value: the heat of formation of $Cu_2O + \frac{1}{2} O_2 = 2 CuO$ is $-35,000$ cal according to Dulong,¹⁰⁾ and

where v is the velocity of a molecule (cm/sec) and n the number of the molecules in 1 c.c.
At $298^\circ K$,

$$v = 4.104^4$$

$$\text{At } 0.292 \times 10^{-26} \text{ atm,}$$

$$n_0 = 3 \times 10^{19} \times 0.292 \times 10^{-26}$$

$$= 8.76 \times 10^{-8}$$

$$\therefore n = 4 \times 10^4 \times 8.76 \times 10^{-8}$$

$$= 3.5 \times 10^{-3}$$

7) S. Horiba and N. Hayami, *loc. cit.*

8) Lewis; *Thermodynamics*, 465.

9) Lewis; *Ibid.* 477.

10) Dulong; *Compt. rend.* 7, 87 (1848).

-36,200 cal. according to Andrews¹¹⁾, which differ more or less from the value obtained.

Similarly, $(\Delta F)_{298}^H$ and $(\Delta H)_{298}^H$ of some intensities of light were calculated. The values obtained are given in Table XV and Fig. XII. It is apparent from the figure that the relation between both ΔF and ΔH and the intensity of light is linear.

Table XV.

The Influence of Intensity of Light on ΔF and ΔH at 25°C.

Intensity of light (cal/cm ² /sec)	E. M. F. of Cell [A] (volts) obs.	Cell $\text{Cu} \text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10} \text{NaOH} \text{H}_2$ (volts) calc.	$(\Delta F)_{298}$ (calc.)	$(\Delta H)_{298}$ (calc.)	$\Delta S = \frac{\Delta H - \Delta F}{T}$ $\text{Cu}_2\text{O} + \frac{1}{2}\text{O}_2 = 2\text{CuO}$
0	0.2323	0.8424	-17620	-22440	-15.20
0.002318	0.2298	0.8449	-17565	-22350	-16.12
0.004055	0.2282	0.8465	-17496	-22270	-16.05
0.00813	0.2233	0.8514	-17170	-22124	-16.63
0.02843	0.2174	0.8573	-17039	-21820	-16.05
0.1042	0.2087	0.8660	-16596	-21400	-16.15
5.575	0.1848	0.8899	-15493	-20420	-16.54
14.100	0.1628	0.9119	-14478	-19520	-16.93

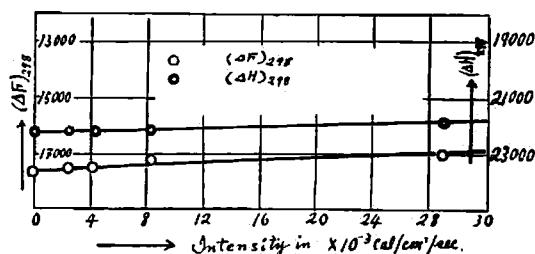


Fig. 12

The influence of intensity of light on ΔF and ΔH at 25°C.

2) Equilibrium Constant.

In order to measure the equilibrium voltage of the cell, $\text{Cu}|\text{Cu}_2\text{O}, \text{CuO} \frac{\text{N}}{10}$

$\text{NaOH}|\text{H}_2$, the equilibrium constant of $4\text{CuO} \rightleftharpoons 2\text{Cu}_2\text{O} + \text{O}_2$ was measured, using the following equation:


$$\Delta F = -RT \ln K_{p_{\text{O}_2}} \quad (\text{i})$$

$$\log K_{p_{\text{O}_2}} = -\frac{(-\Delta H)}{4.57 \times 298.1} + \sum n 1.75 \log T + \sum n C \quad (\text{ii})$$

11) Andrews; *Phil. Mag.*, (3), 32, 321 (1848).

$$E_{\alpha} = E_{\beta} + \frac{0.059}{4} \log P_{O_2}; \quad \ln P_{O_2} = \ln K_{P_{O_2}}. \quad (\text{iii})$$

For example, the case in the dark is as follows:



$$(\Delta F)_{298}^0 = 2 \times 17620 = 35,240 \text{ cal.}$$

$$\Delta F = -R T \ln K_{P_1}$$

$$\log K_{P_1} = \frac{-2 \times 17620}{2.303 \times 1.988 \times 298.1} = -25.82,$$

$$K_{P_1} = P_{O_2} = 1.814 \times 10^{-26} \text{ atm.}$$

From equation (ii),

$$\log K_{P_{O_2}} = -\frac{2 \times 22440}{4.571 \times 298.1} + 1.75 \log 298.1 + 2.8 = -25.72$$

$$\therefore K_{P_2} = 1.905 \times 10^{-26} \text{ atm.}$$

And from equation (iii),

$$\log P_{O_2} = \frac{4 \times (0.8424 - 1.226)}{0.059} = -26.00$$

$$\therefore P_{O_2} = 10.0 \times 10^{-26} \text{ atm.}$$

Similarly, the equilibrium constants in the case of different intensities of light can be obtained. Those values are in good agreement as given in Table XVI and Fig. XIII.

Table XVI.
Equilibrium Constant and Intensity of Light.

Number of Expt.	J_{abs} (cal/cm ² /sec.)	S_{exp} (calc. from Table)	$E_{\alpha} = E_{\beta} + \frac{0.059}{4} \log P_{O_2}$	$K_{P_{O_2}}$ ($-\Delta F = RT \ln K_{P_1}$)	$K_{P_{O_2}}$ (Nernst's Formula)
1	0.00	15.18	1.000×10^{-26}	1.814×10^{-26}	1.905×10^{-26}
2	0.002318	14.73	1.514 "	1.405 "	2.042 "
3	0.004055	14.76	1.862 "	2.399 "	2.692 "
4	0.00813	14.47	3.981 "	6.918 "	4.266 "
5	0.02843	14.76	1.000×10^{-25}	1.047×10^{-25}	1.349×10^{-25}
6	0.1042	14.71	3.981 "	5.012 "	4.266 "
7	5.575	14.51	1.622×10^{-23}	1.995×10^{-23}	1.349×10^{-23}
8	14.100	14.32	5.012×10^{-22}	6.206×10^{-22}	3.020×10^{-22}


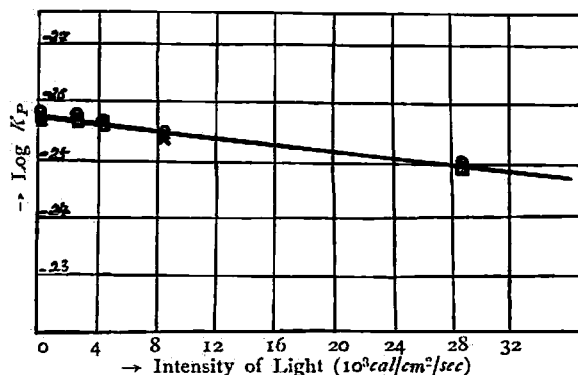


Fig. XIII
Equilibrium Constant (at 25°C.)

- Log P_{O_2}
- × Log K_{P_1}
- Log K_{P_2}

3) Entropy.

In the dark,



$$(\Delta F)_{298}^D = -17,620 \text{ cal}; \quad (\Delta H)_{273}^D = -2244 \text{ cal}$$

$$\therefore \Delta S = \frac{\Delta H - \Delta F}{T} = 15.20 \text{ (Entropy Unit)}.$$

Accordingly, the value of S_{CuO} will be as follows:

$$-15.20 = S_{\text{CuO}} - S_{\frac{1}{2}\text{O}_2} - S_{\text{Cu}_2\text{O}}$$

$$= 2 S_{\text{CuO}} = 24.1^{12)} - 21.46$$


$$\therefore S_{\text{CuO}} = 15.18 \text{ (Entropy Unit)}.$$

Table XVI gives the values in the light.

S_{CuO} was calculated in another way. From the temperature coefficient of the voltage of the $\text{Cu}|\text{Cu}_2\text{O}, \text{CuO} \frac{N}{10} \text{NaOH}, \text{HgO}|\text{Hg}$ cell ($=0.00017 \text{ volt}^{13)}$ and from the following equation:

$$\Delta S = - \frac{d(\Delta F)}{dT} = nF \frac{dE}{dT}$$

we have



$$\Delta S = nF \frac{dE}{dT}$$

$$= 2 \times 23,074 \times 0.000170 = 7.84 \text{ (Entropy Unit)}.$$

And from the value, $S_{\text{Cu}} = 8.18^{14)}$, $S_{\text{HgO}} = 16.11^{15)}$ and $S_{\text{Hg}} = 17.8^{16)}$,12) Lewis; *Thermodynamics*, 452 (Calculated from sp. ht.)13) S. Horiba and N. Hayami, *loc. cit.*14) Lewis; *ibid.*, 464.15) S_{HgO} was obtained thus:

$$\text{Hg} + \frac{1}{2}\text{O}_2 = \text{HgO} \quad (\Delta F)_{298}^D = -13,804 \text{ cal.}$$

$$(\Delta H)_{298}^D = -21,489 \text{ cal.}$$

$$\therefore \Delta S = \frac{-21,489 + 13,804}{298.1} = -25.79 \text{ (Entropy Unit)}.$$

Hence,

$$-25.79 = S_{\text{HgO}} - 17.8^{11)} - 24.1,$$

$$\therefore S_{\text{HgO}} = 16.11 \text{ (Entropy Unit)}.$$

This value coincides with $S_{\text{HgO}} = 16.3^{12)}$ (Gunther), $S_{\text{HgO}} = 16.2$ 1) Lewis; *Thermodynamics*, 495.2) Lewis; *ibid.*16) Lewis; *Thermodynamics*, 465.

$$S_{CuO} = 7.84 + 8.18 + 16.11 - 17.8 \\ = 14.33 \text{ (Entropy Unit).}$$

It is observed that this value agrees, on the whole, with those obtained from ΔF and ΔH .

Summary.

1) A heterogeneous electrode, $\text{Cu} \left| \text{Cu}_2\text{O}, \text{CuO} \frac{N}{10} \text{NaOH} \right.$, which was in equilibrium in the dark has been assumed to be a kind of reversible reaction system and the chemical kinetics of reactions in the dark and in the light has proved to be applicable to such a heterogeneous system. The velocity equation of the reaction system at any wave length and intensity of light is given by

$$\frac{d(\Delta P)}{dt} = k_1 \cdot J_{\text{abs}} - k'_1 [O_2],$$


and it has been ascertained that the velocity formula of the reaction in the dark satisfies the reaction of the first order:

$$-\frac{d(\Delta P')}{dt} = k'_1 [O_2],$$

and the formula of the photochemical reaction, excluding the reaction in the dark, satisfies that of the zero order:

$$\frac{dP}{dt} k_1 \cdot J_{\text{abs}} = k'_1.$$

2) On the other hand, making thermodynamical research on the said reaction system, the equilibrium constants in the light and the dark have been calculated from the formulae and they have proved to be in good agreement. Further thermodynamical constants have been calculated. Hence the entropy in the case of the formation of CuO , which has been proved to agree fairly well with the theoretical value. Thus, it has been experimentally demonstrated that the Becquerel effect of copper oxide electrode in alkali solution is brought about according to the photochemical reversible reaction of a heterogeneous system:



The author takes this opportunity to express his deep gratitude to Professor S. Horiba for his continued guidance.

*The Laboratory of Physical Chemistry,
Kyoto Imperial University.*